

# THE INFLUENCE OF DEICING SALT ON AIR VOIDS OF ASPHALT MIXTURE UNDER FREEZE-THAW CYCLE

Vinnitsa National Technical University

*The extensive use of deicing salt has not only solved the problem of road icing but also had a serious impact on the pavement, reducing its lifespan. In order to deeply understand the impact of deicing salt on the air voids of asphalt mixture in the northwest climate of China, this paper conducted freeze-thaw cycle tests on AC-13 and AC-16 asphalt mixtures under three different deicing salt solutions and three different low-temperature environments, and analyzed the changes in air voids, meanwhile, the Logistic prediction model was used to evaluate the change characteristics of the air voids. The experimental results showed that the air voids of asphalt mixture increased to varying degrees after multiple freeze-thaw cycles; when the temperature was above its freezing point, no frost heave damage occurred, and the air voids increased slowly; when the temperature was below the freezing point, frost heave damage occurred, causing rapid growth and connection of voids in the mixture, and the air voids increased rapidly; the Logistic model showed a good fit with the observed changes in air voids.*

**Key words:** asphalt mixture, freeze-thaw cycle, air voids, deicing salt.

## Introduction

With the rapid development of society, more and more roads have been paved with asphalt concrete [1-2]. However, as the impact of global climate change intensifies, winter maintenance of roads in cold regions has become an important issue [3]. The main method of winter road maintenance is to spread deicing salt when the road is frozen, but the long-term and excessive use of deicing salt also increases the damage to road materials [4-5].

Air voids is one of the important indicators for evaluating the performance of asphalt mixtures [6]. The size of the air voids directly affects the frost resistance and durability of asphalt mixture, and reducing the air voids appropriately is an effective way to improve their performance. Scholars have conducted some related research on the influence of air voids, JOHN T [7] believes that lower air voids is beneficial for both fatigue life and initial stiffness. Jing Hu [8] found through a study of the internal structure of asphalt mixture that different porosity distributions and shapes have a significant impact on the failure state of asphalt mixture. Yanjing Zhao [9] proved through CT scanning images that non-connected pores in asphalt concrete mainly distribute near the center of the specimen, and connected pores are distributed slightly closer to the outer edge. Tao Ma [10] investigated the influence of structural parameters such as air voids, pore size, and pore distribution on the creep behavior of asphalt mixtures and found that the more and larger the pores, the greater the creep strain of the asphalt mixture, in addition, the uneven distribution of pores in asphalt mixture also has a negative impact on their creep deformation. However, these studies did not consider the variation of porosity under salt dissolution conditions.

On the basis of the special climate in northwest China [11-12], this paper uses collected data on rainfall, air humidity, and temperature between pavement layers to conduct freeze-thaw cycle tests on two types of asphalt mixture with three deicing salt solutions of suitable concentration and in three low-temperature environments. The study aims to investigate the mechanism of the effect of deicing salt on the air voids of asphalt mixtures and to propose corresponding measures to reduce the damage caused by deicing salt to asphalt mixtures, providing a reference for road design and maintenance.

## Experimental materials and methods

In this experiment, KL-90 petroleum asphalt was selected, and its various technical indicators were determined to meet the requirements of the specifications, as shown in Table 1. The technical indicators of the selected coarse and fine aggregates and mineral powder also met the specifications, as shown in Tables 2 - 4.

Table 1

**Technical indexes of asphalt**

Index	Test Result	Requirement	Test Method
Penetration (25 °C, 100 g.5s)/0.1 mm	88.5	80~100	T0604
Penetration Index	-0.9	-1.5~+1.0	T0604
Softening Point/°C	49	≥45	T0606
Flash Point/°C	303	≥245	T0611
Extensibility (15 °C)/cm	147	≥100	T0605
Density (15 °C)/(g·cm-3)	1.034	—	T0603
Dynamic viscosity (60°C)/Pa·s	153	≥140	T0620
Solubility/%	99.8	≥99.5	T0607

Table 2

**Technical indicators of coarse aggregate**

Index	Test Result	Requirement	Test Method
Crushed Stone Value/%	17.6	≤28	T0316
Los Angeles Abrasion Loss/%	17.5	≤30	T0317
Apparent Particle Density	2.82	≥2.5	T0304
Solmdness/%	10.8	≤12	T0314
Water Absorption/%	1.5	≤3	T0304

Table 3

**Technical indicators of fine aggregate**

Index	Test Result	Requirement	Test Method
Apparent Particle Density	2.74	≥2.50	T0328
Sand Equivalent/%	75	≥60	T0334
Solmdness/%	9.2	≤12	T0340
Mud Content/%	2.0	≤3	T0333

Table 4

**Technical indicators of mineral powder**

Index	Test Result	Requirement
Density/(t·m-3)	2.82	≥2.5
Water Absorption/%	0.88	≤1
Hydrophilic Coefficient/%	≤1	≤1
Appearance	No agglomerates	No agglomerates

For this experiment, two types of dense-graded asphalt mixture, AC-13 and AC-16, were selected. The target gradation curves are shown in Figures 1 - 2.

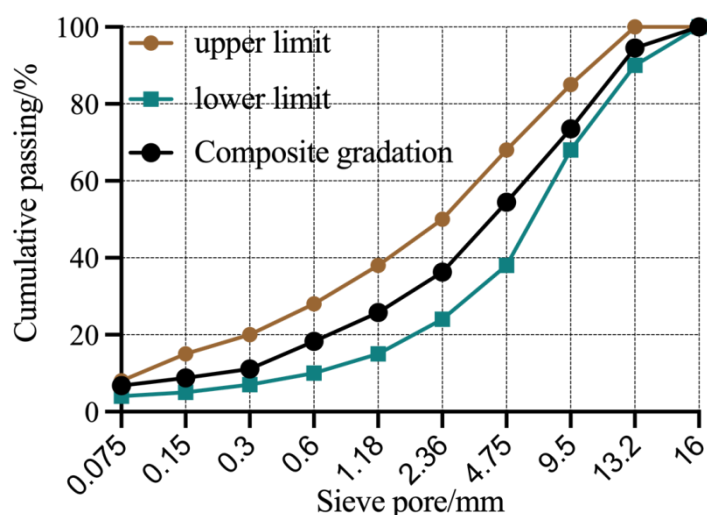


Fig.1 Synthetic grading curve of AC-13

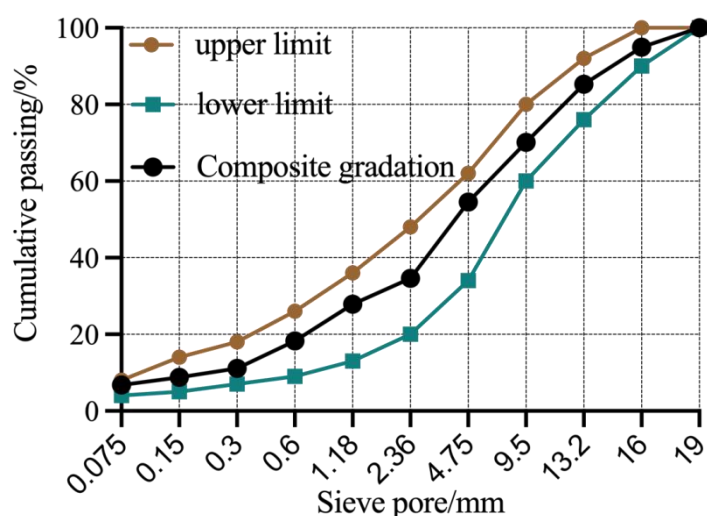


Fig.2 Synthetic grading curve of AC-16

On the basis of considering the deicing effect and economy, the experiment adopted 20% industrial salt (NaCl), 15% urea ( $\text{CH}_4\text{N}_2\text{O}$ ) and 20% anhydrous ethanol ( $\text{CH}_2\text{CH}_3\text{OH}$ ) as the solutions for the freeze-thaw cycles, respectively. Marshall specimens of two types of gradations, AC-13 and AC-16, were prepared and subjected to freeze-thaw cycle tests with 0, 5, 10, 15, 20, 25, and 30 cycles at temperatures of  $-5^\circ\text{C}$ ,  $-15^\circ\text{C}$ , and  $-25^\circ\text{C}$ . Each cycle included immersion in the three solutions for  $12 \pm 0.5$  hours and subsequent placement in the temperature controlled cabinet for  $12 \pm 0.5$  hours. After the completion of the freeze-thaw cycles, the air voids of the asphalt mixture were determined according to the "Standard Test Methods for Bitumen and Bituminous Mixtures for Highway Engineering" (JTG E20-2011).

### Results analysis and discussion

The results of air voids and its growth rate of AC-13 asphalt mixture after freeze-thaw cycles in three different deicing salt solutions and three different low temperature environments are shown in Figure 3.

From Figures 3(a) and 3(b), it can be seen that when the gradation of asphalt mixture is AC-13 and the freezing temperature is  $-5^\circ\text{C}$ , the air voids corresponding to the three types of deicing salt solutions shows an increasing trend with the increase of freeze-thaw cycles, and the temperature at this time did not fall below the freezing point of the three deicing salt solutions, so the growth rate is slow. Among them,  $\text{CH}_4\text{N}_2\text{O}$  has the greatest influence on the air voids, and its corresponding air voids increased by 39.25% to 6.28% in the 30th cycle, which no longer meets the air voids requirements of some pavements. NaCl has the second largest influence on the air voids, and its corresponding air voids increased by 19.51% to 5.39% in the 30th cycle.  $\text{CH}_2\text{CH}_3\text{OH}$  has the smallest influence on the air voids, and its corresponding air voids increased by 13.97% to 5.14% in the 30th cycle.

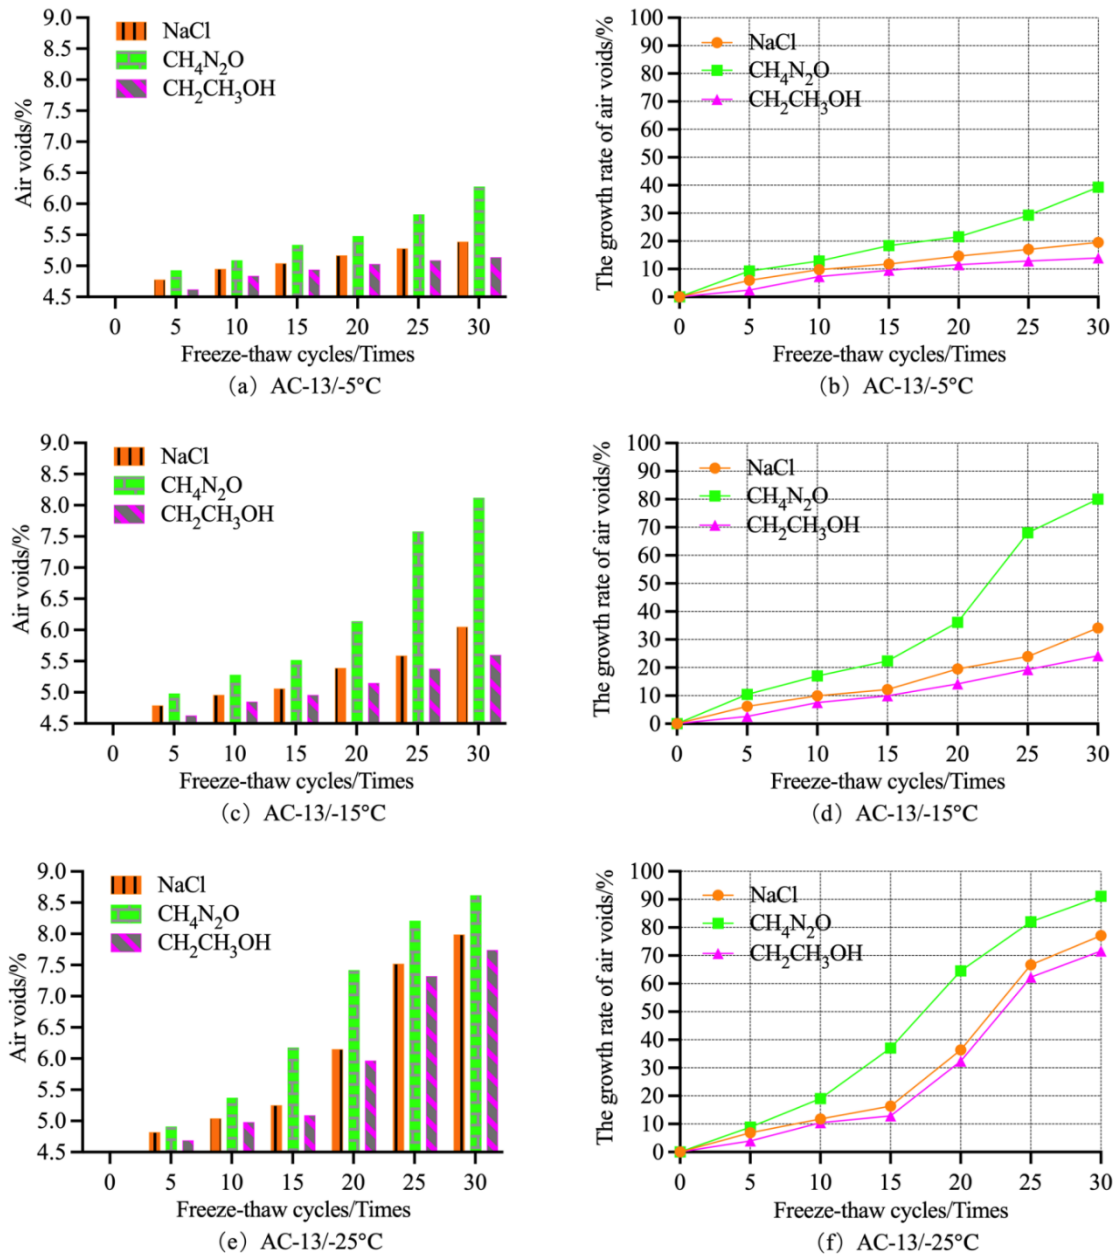


Fig. 3 Variation of air voids with increasing number of freeze-thaw cycles

From Figure 3(c) and 3(d), it can be seen that when the gradation of asphalt mixture is AC-13 and the freezing temperature is  $-15^{\circ}\text{C}$ , the air voids of the three types of deicing salt solutions increases with the number of freeze-thaw cycles, and the air voids corresponding to  $\text{CH}_4\text{N}_2\text{O}$  starts to increase rapidly from the 20th cycle, with a much higher growth rate than that of NaCl and  $\text{CH}_2\text{CH}_3\text{OH}$ . At this point, the temperature has dropped below the freezing point of the solution of  $\text{CH}_4\text{N}_2\text{O}$ , and condensation occurs. In the 30th cycle, the corresponding air voids of  $\text{CH}_4\text{N}_2\text{O}$  increased by 80.04%, reaching 8.12 %, which no longer meets the requirements for air voids of road. NaCl has the second largest impact on air voids, and its corresponding air voids increased by 34.15 % in the 30th cycle, reaching 6.05 %.  $\text{CH}_2\text{CH}_3\text{OH}$  has the smallest effect on air voids, and its corresponding air voids increased by 24.17 % in the 30th cycle, reaching 5.60 %.

From Figure 3(e) and 3(f), it can be seen that when the gradation of asphalt mixture is AC-13 and the freezing temperature is  $-25^{\circ}\text{C}$ , the air voids of the three deicing salts increases with an increase in the number of freeze-thaw cycles. The air voids corresponding to the three deicing salts start to increase rapidly from the 15th cycle, when the temperature is below the freezing point of all three deicing salt solutions, and condensation occurs. Among them,  $\text{CH}_4\text{N}_2\text{O}$  has the greatest impact on the air voids, with its corresponding air voids increasing by 91.13 % in the 30th cycle, reaching 8.62 %. The effect of NaCl on the air voids is second, with its corresponding air voids increasing by 77.16 % in the 30th cycle, reaching 7.99 %. The effect of  $\text{CH}_2\text{CH}_3\text{OH}$  on the air voids is the smallest, with its corresponding air voids increasing by 71.62 % in the

30th cycle, reaching 7.74 %.

The results of air voids and its growth rate of AC-16 asphalt mixture after freeze-thaw cycles in three different deicing salt solutions and three different low temperature environments are shown in Figure 4.

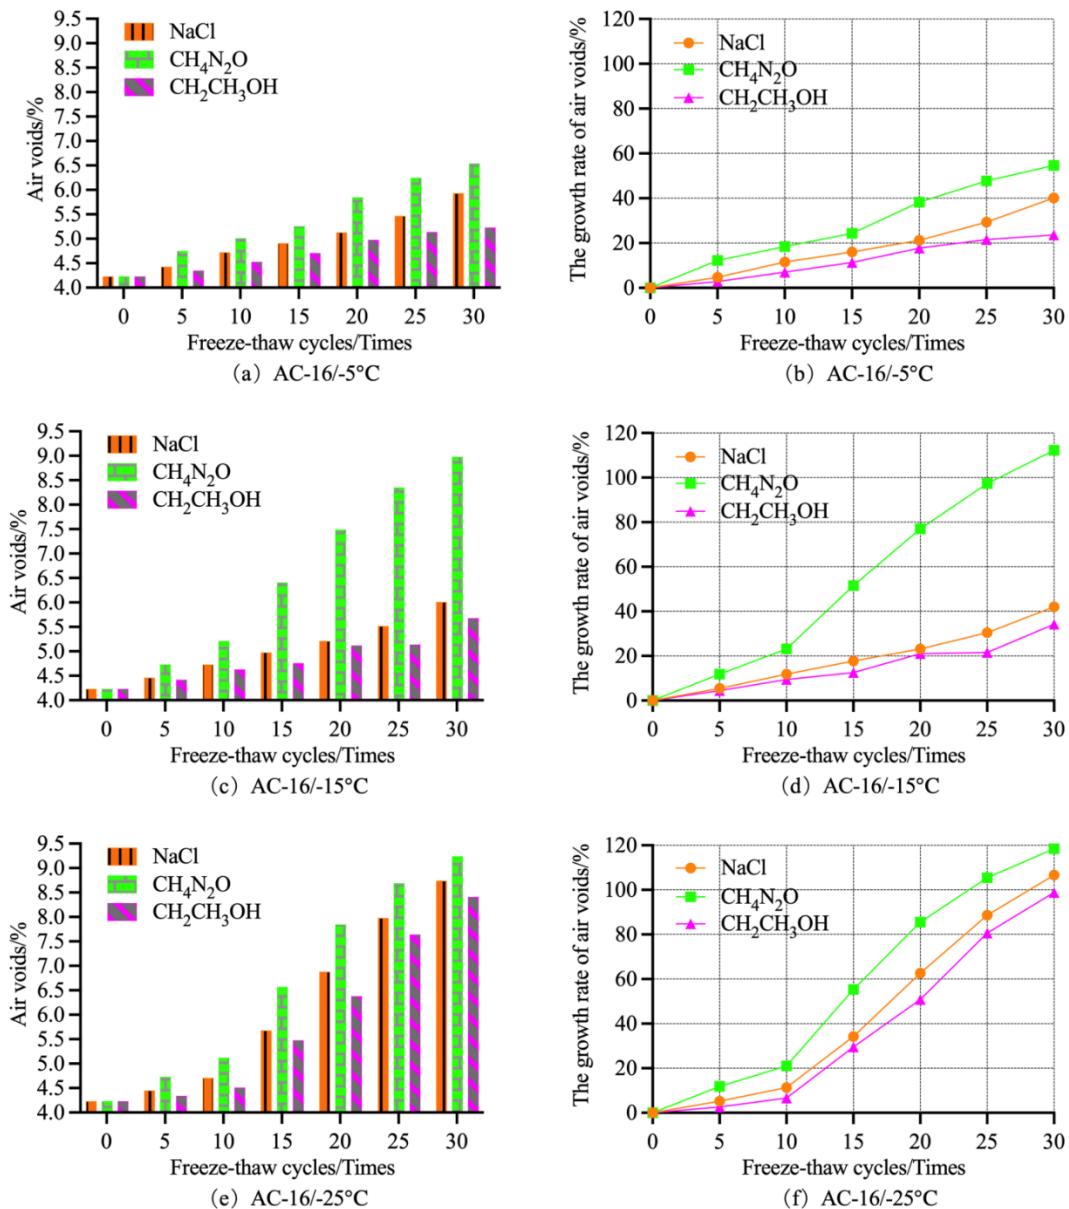


Fig. 4 Variation of air voids with increasing number of freeze-thaw cycles

From Figures 4(a) and 4(b), it can be seen that when the gradation of asphalt mixture is AC-16 and the freezing temperature is -25°C, as the number of freeze-thaw cycles increases, the corresponding air voids for the three types of deicing salts shows a growing trend, and the growth rates are slow as the temperature has not fallen below the freezing point of the three deicing salt solutions. Among them, CH<sub>4</sub>N<sub>2</sub>O has the greatest impact on the air voids, with an increase of 54.61 % at the 30th cycle, reaching 6.54 %, which no longer meets the requirements of certain pavement. The effect of NaCl on air voids is secondary, with an increase of 40.19% at the 30th cycle, reaching 5.93 %. The effect of CH<sub>2</sub>CH<sub>3</sub>OH on air voids is the smallest, with an increase of 23.64 % at the 30th cycle, reaching 5.23 %.

From Figures 4(c) and 4(d), it can be seen that for the AC-16 asphalt mixture, when the freezing temperature is -15°C, the air voids corresponding to the three types of deicing salt solutions shows an increasing trend with the increase of freeze-thaw cycles. The air voids corresponding to the solution of CH<sub>4</sub>N<sub>2</sub>O increases rapidly starting from the 20th cycle, with an increase rate far higher than that of NaCl and CH<sub>2</sub>CH<sub>3</sub>OH, and at this point, the temperature has already dropped below the freezing point of the solution of CH<sub>4</sub>N<sub>2</sub>O, and condensation phenomenon occurs. At the 30th cycle, the corresponding air voids of CH<sub>4</sub>N<sub>2</sub>O increased by 112.29 %, reaching 8.98 %, which can no longer meet the requirements of the pavement. The impact of NaCl

on the air voids is second, and at the 30th cycle, the corresponding air voids increases by 42.08 %, reaching 6.01%. The impact of CH<sub>2</sub>CH<sub>3</sub>OH on the air voids is the smallest, and at the 30th cycle, the corresponding air voids increases by 34.27 %, reaching 5.68 %.

From Figure 4(e) and 4(f), it can be seen that when the gradation of asphalt mixture is AC-16 and the freezing temperature is -25°C, the air voids of the three types of deicing salts all show an increasing trend with the increase of freeze-thaw cycles, and the air voids of the three types of deicing salts all starts to increase rapidly from the 15th cycle, at which point the temperature is lower than the freezing point of the three deicing salt solutions, and condensation occurs. Among them, CH<sub>4</sub>N<sub>2</sub>O has the greatest influence on air voids, and its corresponding growth rate reached 118.44 % at the 30th cycle, reaching 9.24 %; NaCl has the second greatest influence on air voids, and its corresponding growth rate reached 106.62 % at the 30th cycle, reaching 8.74 %; CH<sub>2</sub>CH<sub>3</sub>OH has the smallest influence on air voids, and its corresponding growth rate reached 98.82 % at the 30th cycle, reaching 8.41 %.

Based on Figures 3 and 4, it can be observed from the growth rate of air voids with the increase of freeze-thaw cycles that regardless of whether the freezing point of the deicing salt solution is reached or not, that is, whether it freezes or not, the rate of increase of AC-16 is higher than that of AC-13, moreover, the percentage of fine aggregate in AC-13 is higher than that in AC-16, which means that increasing the percentage of fine aggregate can slow down the speed of void damage and connectivity in asphalt mixtures.

### Prediction models for air voids

In this paper, Logistic prediction model was constructed using two independent variables, x and y, to represent temperature and freeze-thaw cycles, respectively, and the air voids was used as the dependent variable:

$$R_T = \frac{a}{\left[1 + \exp\left(\frac{b-x}{m}\right)\right] \left[1 + \exp\left(\frac{c-y}{n}\right)\right]} + d$$

In this equation, a, b, c, d, m, and n are fitting parameters.  $R_T$  is a function that varies with x and y. Through numerical simulation, the Logistic prediction models were fitted under various conditions, and the results are shown in Table 5.

Table 5

#### Variance analysis of different influencing factors and air voids

Types of Deicing Salt	Gradation	Logistic prediction model	Correlation coefficient R <sup>2</sup>
NaCl	AC-13	$R_T = \frac{26.6}{\left[1 + \exp\left(\frac{21.81-x}{1.366}\right)\right] \left[1 + \exp\left(\frac{-21.05-y}{2.298}\right)\right]} + 4.574$	0.9379
CH <sub>4</sub> N <sub>2</sub> O	AC-13	$R_T = \frac{1.415}{\left[1 + \exp\left(\frac{1.061-x}{0.7981}\right)\right] \left[1 + \exp\left(\frac{0.8903-y}{3.712}\right)\right]} + 3.869$	0.95
CH <sub>2</sub> CH <sub>3</sub> OH	AC-13	$R_T = \frac{9.653}{\left[1 + \exp\left(\frac{16.32-x}{1.14}\right)\right] \left[1 + \exp\left(\frac{-15.91-y}{2.069}\right)\right]} + 4.582$	0.9357
NaCl	AC-16	$R_T = \frac{14.31}{\left[1 + \exp\left(\frac{22.41-x}{1.645}\right)\right] \left[1 + \exp\left(\frac{-22.33-y}{2.648}\right)\right]} + 4.13$	0.9161
CH <sub>4</sub> N <sub>2</sub> O	AC-16	$R_T = \frac{3.044}{\left[1 + \exp\left(\frac{0.7394-x}{0.4165}\right)\right] \left[1 + \exp\left(\frac{1.913-y}{4.929}\right)\right]} + 2.61$	0.9453
CH <sub>2</sub> CH <sub>3</sub> OH	AC-16	$R_T = \frac{9.596}{\left[1 + \exp\left(\frac{15.02-x}{1.175}\right)\right] \left[1 + \exp\left(\frac{-15.8-y}{2.309}\right)\right]} + 4.24$	0.9294

From Table 5, it can be seen that, under the coupling effect of multiple factors, the variation of air voids in the asphalt mixture is well correlated with the Logistic model, and the correlation coefficients are all above



0.91. Therefore, the Logistic model can effectively reflect the changing trend of air voids over time.

### Conclusions

By conducting freeze-thaw cycle tests on AC-13 and AC-16 under three different low-temperature environments and three different deicing salt solutions, the following conclusions can be drawn by analyzing the variation of air voids:

(1) The influence of deicing salts on the air voids of asphalt mixtures, from large to small, follows the order of  $\text{CH}_4\text{N}_2\text{O} > \text{NaCl} > \text{CH}_2\text{CH}_3\text{OH}$ .

(2) The erosion resistance of AC-13 is higher than that of AC-16, indicating that increasing the percentage of aggregate can slow down the rate of void damage and connectivity in asphalt mixtures.

(3) When deicing salt solution infiltrates the interior of the asphalt mixture, it can cause erosion damage to the mixture even at temperatures above its freezing point, but frost heaving damage will occur when the temperature drops below its freezing point, which can lead to rapid growth and connectivity of voids in the mixture, seriously affecting the pavement's service life.

(4) The Logistic model shows good correlation with the change of air voids, with correlation coefficients greater than 0.91.

### REFERENCES

- Mingjun, Guo. "Safety measures for driving on icy roads in winter." *Матеріали Всеукраїнської науково-практичної конференції курсантів і студентів "Наука про цивільний захист як шлях становлення молодих вчених 13: 266-267.*
- Yanqiu, F., et al., Discussion on the Influence of Road Traffic Safety Facilities on Traffic Safety. *Technological Innovation and Application*, 2019. 27.
- Kalafat K. Technical research and development [Text]: collective monograph / Kalafat K., Vakhitova L., Drizhd V., etc. – International Science Group. – Boston, : Primedia eLaunch 2021. – 616 p.
- Guo Mingjun. Research progress on hydrodynamic pressure of asphalt pavement [Електронний ресурс] / Guo Mingjun, I. V. Khomyuk, V. P. Kovalskiy // *Матеріали Всеукраїнської науково-практичної інтернет-конференції «Молодь в науці: дослідження, проблеми, перспективи (МН-2022)»*, Вінниця, 16-17 червня 2022 р. – Електрон. текст. дані. – 2022. – Режим доступу: <https://conferences.vntu.edu.ua/index.php/mn/mn2022/paper/view/16326>.
- Guo Mingjun Research of mechanical properties of bituminous concrete at low-temperature [Text] / Guo Mingjun, V. P. Kovalskiy // *Applied Scientific and Technical Research : proceedings of the IV International Scientific and Practical Conference*, Ivano-Frankivsk, April 1–3, 2020. – Ivano-Frankivsk : Vasyl Stefanyk Precarpathian National University, 2020. – V. 2. – P. 104-105.
- Мінцзюнь Г. Overview of the test method for road pavement at high temperatures [Електронний ресурс] / Г. Мінцзюнь, В. П. Ковальський // *Матеріали XLIX науково-технічної конференції підрозділів ВНТУ, Вінниця, 27-28 квітня 2020 р.* – Електрон. текст. дані. – 2020. – Режим доступу: <https://conferences.vntu.edu.ua/index.php/all-fbtegp/all-fbtegp-2020/paper/view/8817>.
- Mingjun G. Review of road geothermal snow melting technology [Електронний ресурс] / G. Mingjun, V. Kovalskiy // *Матеріали L науково-технічної конференції підрозділів ВНТУ, Вінниця, 10-12 березня 2021 р.* – Електрон. текст. дані. – 2021. – Режим доступу: <https://conferences.vntu.edu.ua/index.php/all-fbtegp/all-fbtegp-2021/paper/view/12635>.
- Guo Mingjun Research status of road deicing salt [Текст] / Guo Mingjun, V. P. Kovalskiy // *Стратегія розвитку міст: молодь і майбутнє (інноваційний ліфт) : матеріали Міжнародної науково-практичної конференції (квітень 2020 року).* – Харків : Харківський національний університет міського господарства імені О.М. Бекетова, 2020. – С. 292-297.
- Guo Mingjun. Common evaluation methods for water stability of asphalt mixture [Електронний ресурс] / Guo Mingjun, Victor Kovalskiy, Mykhailo Bondar // *Збірник матеріалів Міжнародної науково-технічної конференції «Енергоефективність в галузях економіки України-2021»*, м. Вінниця, 12-14 листопада 2021 р. : електронне мережеве наукове видання. – Електрон. текст. дані. – 2021. – с. 4. – Режим доступу: <https://conferences.vntu.edu.ua/index.php/egcu/egcu2021/paper/viewFile/14092/11941>
- Guo Mingjun. The effect of anti-icing reagents on the frost resistance of asphalt concrete [Електронний ресурс] / Guo Mingjun, M. D. Bondar, V. P. Kovalskiy // *Збірник матеріалів Міжнародної науково-технічної конференції "Інноваційні технології в будівництві (2022)", 23-25 листопада 2022 р.* – Вінниця : ВНТУ, 2022. – <https://conferences.vntu.edu.ua/index.php/itb/itb2022/paper/view/16746>

### REFERENCES

- M. Sukhija and N. Saboo, "A comprehensive review of warm mix asphalt mixtures-laboratory to field," *Construction and Building Materials*, vol. 274, p. 121781, Mar. 2021, doi: 10.1016/j.conbuildmat.2020.121781.
- F. Kaseer, A. E. Martin, and E. Arámbula-Mercado, "Use of recycling agents in asphalt mixtures with high recycled materials contents in the United States: A literature review," *Construction and Building Materials*, vol. 211, pp. 974–987, Jun. 2019, doi: 10.1016/j.conbuildmat.2019.03.286.
- M. Wang, H. Gao, M. Chai, Z. Sun, and J. Wang, "Study on the Performances of an Anticoagulant Ice Coating Material for Asphalt Pavement," *J. Phys.: Conf. Ser.*, vol. 2168, no. 1, p. 012014, Jan. 2022, doi: 10.1088/1742-6596/2168/1/012014.
- K. Liu et al., "Deicing efficiency analysis and economic-environment assessment of a novel induction heating asphalt pavement," *Journal of Cleaner Production*, vol. 273, p. 123123, Nov. 2020, doi: 10.1016/j.jclepro.2020.123123.
- Q. Zhang, D. Wu, X. Zhang, K. Chang, and Y. Wang, "Effect of organic deicing agents on asphalt rheology and analysis of the mechanism," *Construction and Building Materials*, vol. 284, p. 122649, May 2021, doi: 10.1016/j.conbuildmat.2021.122649.

6. S. Chen, Z. You, S.-L. Yang, A. Garcia, and L. Rose, "Influence of air void structures on the coefficient of permeability of asphalt mixtures," Powder Technology, vol. 377, pp. 1–9, Jan. 2021, doi: 10.1016/j.powtec.2020.08.082.
7. J. T. Harvey and B.-W. Tsai, "Effects of asphalt content and air void content on mix fatigue and stiffness," Transportation research record, vol. 1543, no. 1, pp. 38–45, 1996.
8. J. Hu, Z. Qian, D. Wang, and M. Oeser, "Influence of aggregate particles on mastic and air-voids in asphalt concrete," Construction and Building Materials, vol. 93, pp. 1–9, Sep. 2015, doi: 10.1016/j.conbuildmat.2015.05.031.
9. Y. Zhao, X. Wang, J. Jiang, and L. Zhou, "Characterization of interconnectivity, size distribution and uniformity of air voids in porous asphalt concrete using X-ray CT scanning images," Construction and Building Materials, vol. 213, pp. 182–193, Jul. 2019, doi: 10.1016/j.conbuildmat.2019.04.056.
10. T. Ma, D. Zhang, Y. Zhang, Y. Zhao, and X. Huang, "Effect of air voids on the high-temperature creep behavior of asphalt mixture based on three-dimensional discrete element modeling," Materials & Design, vol. 89, pp. 304–313, Jan. 2016, doi: 10.1016/j.matdes.2015.10.005.
11. Ping Li, Xiying Wei, Tengfei Nian, Yang liu, and Yu Mao, "Freezing Point Test of Deicers on Asphalt Pavement in Seasonal Frozen Region Bulletin of the Chinese Ceramic Society," Bulletin of the Chinese Ceramic Society, vol. 38, no. 05. pp. 1561–1567, 2019.
12. Yang liu and Ping Li, "Study on Temperature Field Prediction Model and Anti Icing Technology of Asphalt Pavement in Winter of Gansu Province," Lanzhou University of Technology, 2018.

**Kovalskiy Victor P.** – Candidate of Technical Sciences, Associate Professor of the Department of Construction, Municipal Economy and Architecture Vinnytsia National Technical University, Vinnytsia, e-mail: [kovalskiy.vk.vntu.edu@gmail.com](mailto:kovalskiy.vk.vntu.edu@gmail.com) ORCID 0000-0002-3103-6319.

**Guo Mingjun**, Postgraduate Department of Department of Construction, Urban Management and Architecture, Vinnytsia National Technical University, Vinnytsia, e-mail: [guo19920408@hotmail.com](mailto:guo19920408@hotmail.com) ORCID / 0000-0001-5924-0779

**В. П. Ковальський**  
**Го Мінцзюнь**

## ВПЛИВ ПРОТИОЖЕЛЕДНОЇ СОЛІ НА ПОРИСТІСТЬ АСФАЛЬТОБЕТОНУ ПРИ ПОПЕРЕМІННОМУ ЗАМОРОЖУВАННІ ТА ВІДТАВАННІ

Вінницький національний технічний університет

*Широке використання протиожеледної солі ефективно вирішує проблему ожеледиці на дорогах взимку, але її використання негативно впливає на дорожнє покриття, скорочуючи його термін експлуатації. З метою отримання комплексного розуміння впливу протиожеледної солі на коефіцієнт пористості асфальтових сумішей, в умовах наближених до клімату північно-західного Китаю, було проведено дослідження поперемінного заморожування та відтавання. Дослідження проводились на двох видах асфальтобетонних зразків АС-13 і АС-16 які були насичені у трьох різних розчинах протиожеледної солі та піддавались низькотемпературному впливу при -5, -15 та -25°C. Вивчені та проаналізовані зміни коефіцієнта пористості. Застосована логістична модель прогнозування зміни коефіцієнта пористості, для оцінки характеристик довговічності асфальтобетону.*

*Експериментальні результати свідчать про те, що після кількох циклів заморожування та відтавання в обох видів асфальтобетонних зразків спостерігається зростання коефіцієнта пористості різного ступеня. Коли температура перебуває вище точки замерзання, суміші не піддаються пошкодженню від замерзання, і зростання коефіцієнта порожності відбувається відносно повільно. Однак, при температурі нижче точки замерзання, виникають пошкодження, що призводить до швидкого розширення та з'єднання порожнин всередині сумішей, що призводить до значного збільшення коефіцієнта пористості. Крім того, спостерігається чітка кореляція між логістичною моделлю та зміною коефіцієнта пористості встановленого в результаті проведення досліджень.*

*Ключові слова:* асфальтна суміш, цикл заморожування-відтавання, повітряні порожнини, протиожеледна сіль.

**Ковальський Віктор Павлович** – к.т.н., доцент кафедри будівництва, міського господарства і архітектури, Вінницького національного технічного університету, e-mail: [kovalskiy.vk.vntu.edu@gmail.com](mailto:kovalskiy.vk.vntu.edu@gmail.com) ORCID 0000-0002-3103-6319.

**Го Мінцзюнь**, аспірант кафедри будівництва, міського господарства та архітектури, Вінницький національний технічний університет. e-mail: [guo19920408@hotmail.com](mailto:guo19920408@hotmail.com)